



**COLUMBUS
STAINLESS**
[Pty] Ltd

Technical Brochure

**MOLY FERRITIC
STAINLESS STEELS**

Adding Stainless Quality to life
www.columbusstainless.co.za

Introduction

Moly ferritic stainless steels are chromium stainless steels alloyed with Molybdenum, and can be stabilised with niobium and/or titanium.

Annealed moly ferritics are ductile and can be formed using a large variety of roll forming or mild stretch bending operations as well as the more common drawing and bending operations. They do not harden excessively during cold working.

Being ferritic, they are not susceptible to stress corrosion cracking.

The steels have limited weldability and should not be used in the as-welded condition for dynamic or impact loaded structures. Moly ferritics can undergo grain growth in the heat affected zone of weldments, which may adversely affect the mechanical properties in these zones.

Applications involving welded moly ferritics are thus generally limited to a maximum thickness of 2.5mm. Edge welds are not recommended for applications using moly ferritics.

They are unsuited for use in cryogenic applications as brittle fracture could occur at sub-zero temperatures.

434 is a low carbon, molybdenum containing ferritic stainless steel. With 16% chromium and 1% molybdenum, the steel has better corrosion resistance than 430. 434 has excellent polishing characteristics and is therefore used in applications such as automotive trim.

434 also has good formability and corrosion resistance and this makes it suitable for applications such as dishwasher, kitchen-ware and restaurant equipment, architectural applications (except in coastal environments), nitric acid plant equipment, etc.

436 is a low carbon, niobium stabilised, molybdenum containing ferritic stainless steel. With 16% chromium and 1% molybdenum, the steel has better corrosion resistance than 4509.

Niobium stabilisation improves the steel's resistance to sensitisation in the weld heat affected zone and improves the steel's creep resistance at high temperatures. 436 has similar formability to 4509 and is used in applications such as automotive exhaust systems and trim, cladding, domestic appliances, etc.

444 is a low carbon, dual stabilised, molybdenum containing ferritic stainless steel. With 18% chromium and 2% molybdenum, the steel has good pitting resistance and crevice corrosion resistance, similar to 316L. 444 is thus suitable for roofing and cladding in marine environments, as well as hot water tanks and geysers, heat exchanger tubing and food processing equipment.

Product range

The latest revision of the Product Catalogue should be consulted, as the product range is subject to change without notice.

The Product Catalogue is available from the Technical Department or can be found at www.columbusstainless.co.za

Specifications and tolerances

Columbus Stainless (Pty) Ltd supplies the moly ferritics to ASTM A240 and EN 10088-2.

Columbus Stainless (Pty) Ltd normally supplies material to the following tolerances:

HOT ROLLED

ASTM A480M

ISO 9444 - material processed as coil

ISO 18286 - material processed as plate

ASTM A480/ASTM A480M

ASME ASME SA480/ASME SA480M

ISO 9444-2

EN 10051

EN 10029

IS 6911

COLD ROLLED

ASTM A480M

ISO 9445

ASTM A480/ASTM A480M

ASME SA480/ASME SA480M

ISO 9445-2

IS 6911

Other specifications and tolerances may be available on request. Further information is available in the Product Catalogue, which can be obtained from the Technical Department or can be found at www.columbusstainless.co.za

Further information

TECHNICAL

Columbus Stainless (Pty) Ltd

PO Box 133 • Middelburg • 1050 • South Africa

Tel: +27 (13) 247 3343

Fax: +27 (13) 247 2289

E-mail: technical-help@columbus.co.za

COMMERCIAL

Columbus Stainless (Pty) Ltd

PO Box 133 • Middelburg • 1050 • South Africa

Tel: +27 (13) 247 2020

Fax: +27 (13) 247 2771

E-mail: commercial-help@columbus.co.za

Date of Issue : May 2011

Disclaimer

The material contained in this manual has been designed as a guide for customers of Columbus Stainless (Pty) Ltd. However, the material contained herein is not intended as a substitute for any person's procedures and should not be used or relied upon for any specific or general application without first obtaining competent advice. Furthermore, Columbus Stainless (Pty) Ltd disclaims any responsibility for the suitability of the steel in question for any particular purpose or for the performance or selection of the steel, unless Columbus Stainless (Pty) Ltd specifically and expressly authorises the purpose or selection. The material contained in this manual does not purport to be a comprehensive or exhaustive statement of all relevant material applicable to special and general steel products and no representation, condition or warranty, express or implied, is given by Columbus Stainless (Pty) Ltd as to the accuracy or completeness of this manual and, so far as is permitted by law, Columbus Stainless (Pty) Ltd, its members, staff and consultants disclaim any duty of care in relation to the preparation of this manual and the information that it contains and shall not be liable for any direct, indirect or consequential loss, damage or injury suffered by any person, howsoever caused as a result of relying on any statement in or omission to this manual and any such liability is expressly disclaimed. [Columbus Stainless (Pty) Ltd shall not be liable in the event of a breakdown, malfunction or failure occurring due to faulty design, material or workmanship of the steel, whether based on the information contained herein or not, and shall not, under any circumstances, be liable for any damages, either direct or indirect, particularly consequential damages, including but not limited to damages for loss of profits.]

Chemical composition

In accordance with ASTM A240 and EN 10088-2.

Grade	C	Si	Mn	P	S	N	Cr	Mo	Nb	Ni	Others
434	0.08	1.0	1.0	0.040	0.015		16.0 18.0	0.90 1.25			
436	0.08	1.0	1.0	0.040	0.015	0.04	16.0 18.0	0.80 1.25	7x(C+N)+0.1 0.8		
444	0.025	1.0	1.0	0.040	0.015	0.03	17.5 19.5	1.80 2.50		1.0	Ti: 4x(C+N)+0.2 0.8

- Compositions are ranges or maximum values.
- Stabilisation may be by use of titanium or niobium or zirconium. For ASTM A240, $Ti+Nb>4x(C+N)+0.2$.
For EN 10088-2, according to the atomic mass of these elements and the content of carbon and nitrogen, the equivalence shall be the following:
 Nb (% by mass) = Zr (% by mass) = $7/4$ Ti (% by mass) (i.e. when replacing Ti with Nb , nearly double (1.75) the Nb is needed).

Mechanical properties

In accordance with ASTM A240 and EN 10088-2.

Grade	R _m (MPa)	R _{p0.2} (MPa)	El (%)	Max BHN
434	450 to 630	280	22	
436	480 to 560	300	25	
444	420 to 640	320	20	217

- Minimum values, unless max or range is indicated.
- The table assumes certification to both ASTM A240 and EN 10088-2.

Properties at elevated temperatures

The properties quoted below are typical of annealed moly ferritics. These values are given as a guideline only, and should not be used for design purposes.

Short time elevated temperature tensile strength (MPa)

Grade	100°C	200°C	300°C	400°C	500°C	600°C	700°C
434	500	485	470	450	400	290	130
436	460	400	350	310	260	200	120
444	500	460	440	420	380	300	160

Short time elevated temperature 0.2% proof stress (MPa)

Grade	100°C	200°C	300°C	400°C	500°C	600°C	700°C
434	300	290	280	260	220	160	60
436	280	250	230	200	170	130	80
444	370	330	310	295	270	220	130

Short time elevated temperature elongation (%)

Grade	100°C	200°C	300°C	400°C	500°C	600°C	700°C
434	28	27	24	17	12	14	27
436	28	27	23	20	19	23	35
444	30	28	26	23	21	20	22

Maximum recommended service temperature

Grade	Continuous (°C)	Intermittent (°C)
434	730	870
436	730	870
444	850	950

- In oxidising conditions

Physical properties

The values given below are for 20°C, unless otherwise stated.

	434	436	444	
Density (kg/m ³)	7 740	7 700	7 750	
Modulus of Elasticity in Tension (GPa)	210		220	
Modulus of Elasticity in Torsion (GPa)	65		65	
Specific Heat Capacity (J/kg K)	460	440	430	
Thermal conductivity at	100°C (W/m K)	26.1	26.3	26.8
	500°C (W/m K)	26.3	27.0	27.1
Electrical Resistivity (x10 ⁻⁹ Ω m)	650	580	570	
Mean Coefficient of Thermal Expansion from	0 to 100°C (x10 ⁻⁶ K ⁻¹)	10.4	10.9	10.8
	0 to 300°C (x10 ⁻⁶ K ⁻¹)	11.0	11.9	11.6
	0 to 500°C (x10 ⁻⁶ K ⁻¹)	11.3	12.4	11.9
	0 to 700°C (x10 ⁻⁶ K ⁻¹)	12.1	13.4	12.5
Melting Range (°C)	1 480	1 530	1480	
	1530	1 405	1 495	
Magnetic	Yes	Yes	Yes	

Thermal processing and fabrication

ANNEALING

Annealing is achieved by heating to the following temperatures for 90 minutes per 25mm thickness (3.5min/mm) followed by air quenching. Controlled atmospheres are recommended in order to avoid excessive oxidation of the surface.

	434	436	444
Annealing Temperature (°C)	820 to 920	750 to 850	870 to 970

STRESS RELIEVING

Stress relieving after welding is not normally required. Should this be necessary, temperatures between 200°C and 300°C are recommended for 60 minutes per 25mm thickness (2.5min/mm).

HOT WORKING

Uniform heating of the steel in the range of 950°C to 1 050°C is required. The finishing temperature should be below 750°C and the steel should be cooled rapidly between 550°C and 400°C to prevent 475 embrittlement. Extended holding times above 1000°C should be avoided as excessive grain growth may occur and ductility may be detrimentally affected.

All hot working operations should be followed by annealing and then pickling and passivating to restore the mechanical properties and corrosion resistance.

COLD WORKING

Moly ferritic stainless steels have good formability characteristics with useful mechanical properties. Their good ductility allows them to be readily formed by bending and deep drawing. They do not undergo significant work hardening when cold formed. 434 is slightly more prone to roping than the other moly ferritics.

WELDING


The moly ferritic stainless steels are prone to grain growth in the heat affected zone of weldments. As such, the tensile, fatigue and toughness properties in the welded condition are relatively poor. They should thus not be used for applications where tensile or dynamic loading will be experienced.

The moly ferritics are generally limited to a combined thickness in the welded condition of 2mm for 434, 2.5mm for 436 and 3mm for 444. Edge welds are not recommended.

The use of austenitic filler metals such as types 308L, 309L or 316L will improve the ductility of welds to some extent but all welding procedures should nevertheless endeavour to maintain minimum heat inputs.

The weld discolouration should be removed by pickling and passivating to restore maximum corrosion resistance.

Corrosion resistance

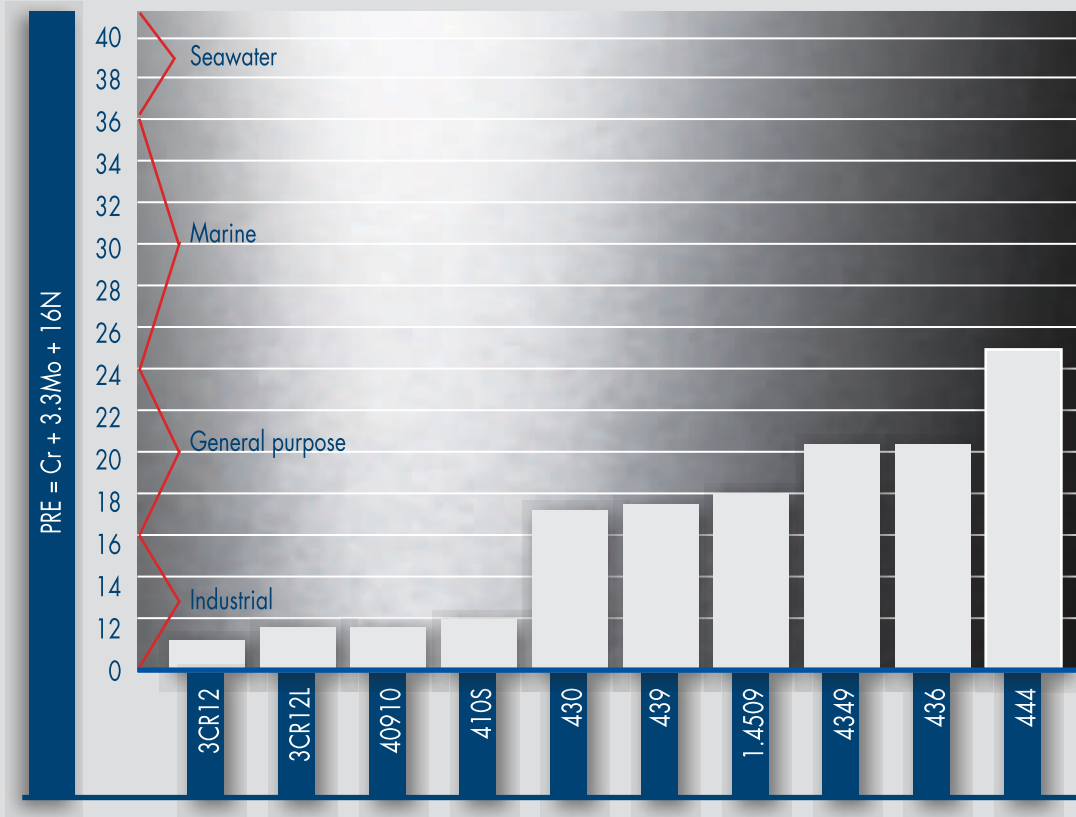

The above diagram summarises the corrosion resistance of the ferritic stainless steels produced at Columbus. For the moly ferritic stainless steels, the corrosion resistance is a function of the chromium and molybdenum contents. In common with the other ferritic stainless steels, the moly ferritics are not susceptible to Stress Corrosion Cracking (SCC).

434 and 436 have similar general corrosion resistance to 430. Their pitting resistance is, however superior to 430 but not as good as 304. 434 and 436 thus have good resistance to rural and industrial atmospheres but in marine atmosphere environments, staining may occur, unless they are regularly washed.

444 has good resistance to a wide variety of corrosive environments. With 18% chromium and 2% molybdenum the steel has good uniform and pitting corrosion resistance, similar to 316L in most environments. 444 is thus suitable for use in marine atmospheres.

For further information, please contact:

TECHNICAL ENQUIRIES

OR

COMMERCIAL ENQUIRIES